

Wr.Nr.	PN	EN	GOST	AISI
1.7131	16HG	16MnCr5	~18XГ	5115

## CHEMICAL COMPOSITION

Chemical composition (in weight %)

Element	C	Si	Mn	P	S	Cr	Cu
min	0.14	0.15	1.00	max.	max.	0.80	max.
max	0.19	0.40	1.30	0.025	0.035	1.10	0.40

## APPLICATION

Parts with predominant high-wear stress which works under medium load, piston pins, levers, worm wheels, bushings, camshafts and other vehicle parts.

## TREATMENT

Jominy test	900 °C ( $\pm 5$ °C) at least 30 min. austenitizing time (reference value)
Carburizing	880 - 980 °C
Direct and single hardening	820 - 860 °C
Core hardening	860 - 900 °C
Case hardening	780 - 820 °C
Tempering	150 - 200 °C mind. 60 min. (approx.)


## ADDITIONAL HEAT TREATMENT

Normalising	840 - 870 °C
Soft annealing	650 - 700 °C
Intermediate annealing	650 - 700 °C


## MECHANICAL PROPERTIES

Modulus of elasticity [GPa]	215
Shear modulus [GPa]	83
Poisson ratio	0,30

## CONTINUOUS COOLING TRANSFORMATION (CCT) DIAGRAM

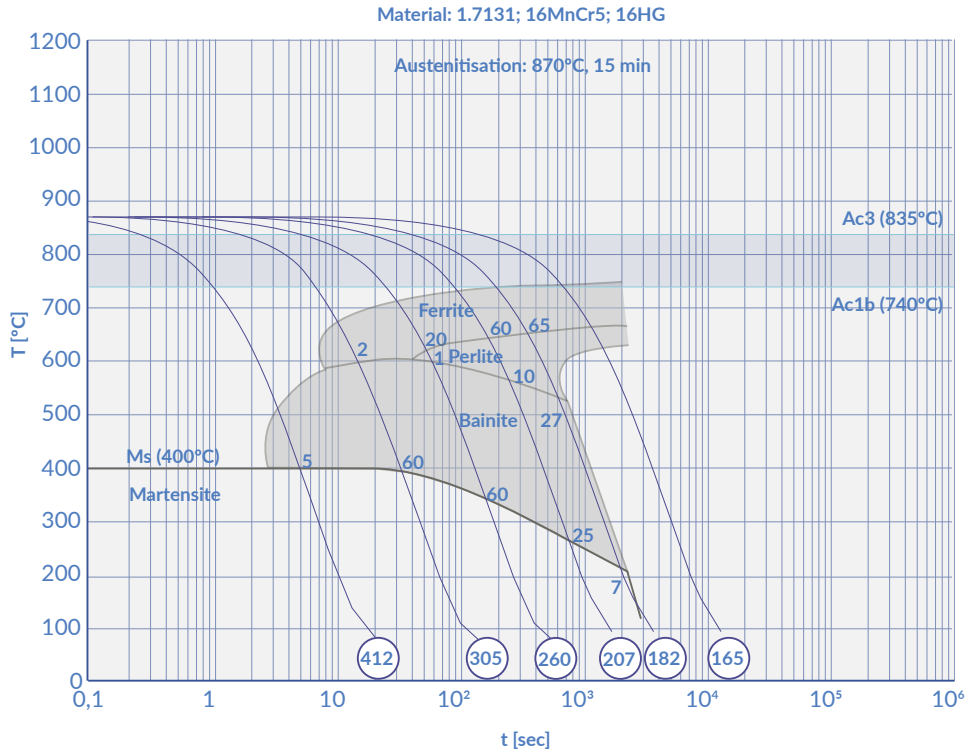

## TEMPERING DIAGRAM

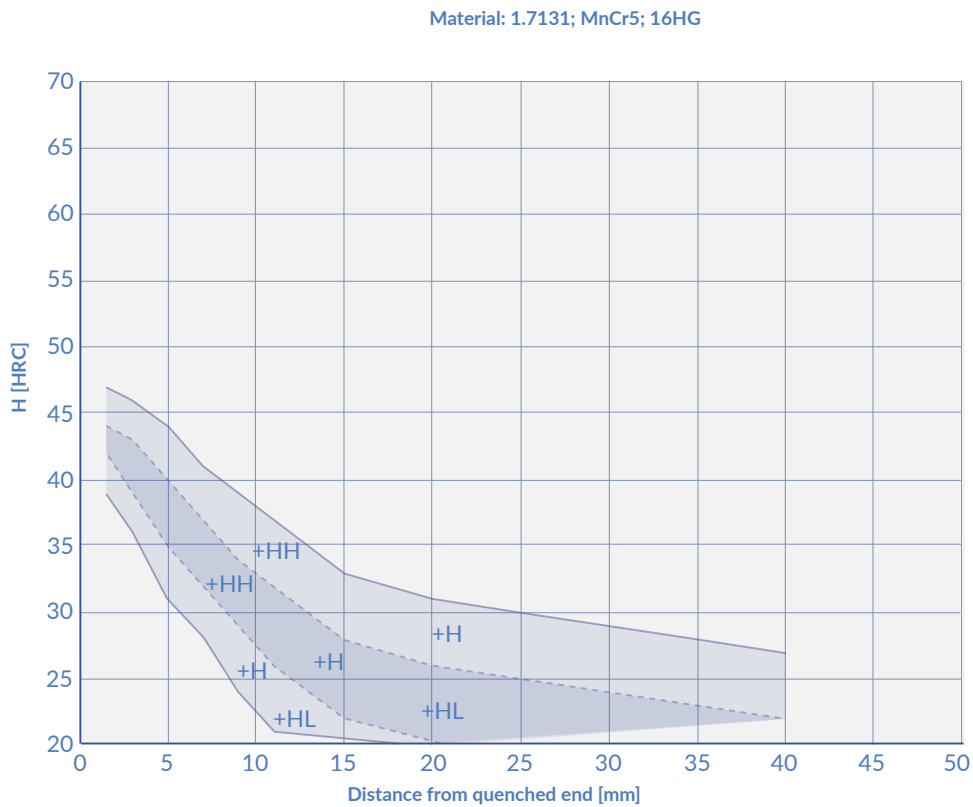

**NOTE:** All technical information is for reference only.